

See discussions, stats, and author profiles for this publication at: <https://www.researchgate.net/publication/290670457>

# Damage Assessment in Concrete Structures using PZT patches

## Damage Assessment in Concrete Structures using PZT patches

CONFERENCE PAPER · DECEMBER 2015

---

READS

10

2 AUTHORS:



[Arun Narayanan](#)

Indian Institute of Technology Hyderabad

2 PUBLICATIONS 0 CITATIONS

[SEE PROFILE](#)



[Kolluru Subramaniam](#)

Indian Institute of Technology Hyderabad

76 PUBLICATIONS 844 CITATIONS

[SEE PROFILE](#)

# Damage Assessment in Concrete Structures using PZT patches

Arun Narayanan and Kolluru V.L. Subramaniam

Department of Civil Engineering, Indian Institute of Technology Hyderabad, INDIA, kvls@iith.ac.in

## Abstract

*Piezoelectric based PZT smart sensors offer significant potential for continuously monitoring the development and progression of internal damage in concrete structures. PZT-based damage sensors consisting of piezo-electric patches, which are bonded to the surface of a concrete structure can be developed for assessing the damage progression of concrete members. The primary challenge in developing a PZT-based sensor lies in developing a methodology to infer about the level of damage in the material from measurement. Changes in the resonant behavior in the measured electrical conductance obtained from electro-mechanical (EM) response of a PZT bonded to a concrete substrate is investigated for increasing levels of damage. The sensitivity of EM impedance-based measurements to level of damage in concrete is reported. Incipient damage in the form of microcracks in the concrete substrate produces a change in the electrical conductance signature associated with the resonant peaks. Changes in the conductance resonant signature from EM conductance measurement are detected before visible signs of cracking. The root mean square deviation of the conductance signature at resonant peaks is shown to accurately reflect the level of damage in the substrate. The findings presented here provide a basis for developing a sensing methodology using PZT patches for continuous monitoring of concrete structures.*

**Keywords:** PZT, impedance, Conductance, Microcracks.

## Introduction

Structural Health Monitoring (SHM) is a process of assessing the structural integrity of the constituent parts and the level of damage level in the structure during its life period. SHM relies on non-destructive evaluation (NDE) procedures and continuous monitoring of structural parameters to determine the intensity and location of the damage. This involves sensors, data acquisition and signal processing tools. Signs of distress in concrete are often associated with visible cracking. Since concrete is a brittle material, which is weak in tension, cracking is the manifestation of damage in the material which results from tensile stress in the material. Stress induced damage in concrete could result from load

application or from internal sources such as shrinkage. Damage initiation takes place in the form of distributed microcracks, which eventually localize to form cracks. Often the damage, particularly in the incipient stages is not directly visible and by the time signs of distress appear on the surface of the structure significant damage would have accrued in the structure and there may be significant degradation of the capacity of the structure. Early detection of damage, before visible signs appear on the surface of the structure is essential to initiate early intervention, which can effectively increase the service life of structures. Methods to detect incipient damage in the form of microcracks are required to provide effective methods of monitoring structural health and service life performance of structures.

Use of PZT patches and wafers has become popular in structural health monitoring. Due to the coupled electro-mechanical constitutive response of a PZT material, the mechanical response of a bonded PZT patch subjected to an applied electrical potential is influenced by the elastic restraint provided by the substrate material. Coupling the structure to the PZT changes the mechanical impedance of the PZT, which produces a change in its vibration characteristics. Monitoring changes in the electrical impedance signature due to changes in the effective mechanical impedance of the substrate is the basis for electromechanical impedance-based measurements. Information about the surrounding material is contained in the electromechanical impedance (EMI) signature of a PZT. By comparing the impedance signature taken in the pristine state and at any other time, structural damage can be determined. Generally, both frequency and amplitude shifts are produced relative to the pristine state (without damage). [Chaudhry et al. (1994), Sun et al. (1995), Ayres et al (1998), Giurgiutiu et al (1997, 1999), Park et al (2000), Zagari (2001), Giurgiutiu (2002, 2004), Peairs (2004)].

Application of EMI technique for damage detection in concrete structures requires a careful study of the changing compliance of the substrate for different forms of damage in the substrate material from the incipient to the visible stages. The use of PZTs for health monitoring of concrete structure was demonstrated by the ability of EMI technique to register changes due to formation of cracks well in advance of failure [Park et al. (2000)]. Several

other studies of damage in concrete using impedance-based measurements of PZTs have been conducted using embedded defects and artificial damage in the form of machine cuts [Tseng (2004), Lim (2006), Dongyu (2010), Wang (2013)]. The EM impedance method has also been used to determine the location of a crack by inducing crack at different positions and depths and cross correlation as damage index [Wang et al. (2013)]. While the use of artificial damage provides meaningful insight, it is not representative of substrate compliance with stress/load induced damage in the material.

Potential of using electro mechanical impedance based measurements of surface mounted PZT to identify the formation of incipient damage in concrete structures is presented in the paper. The relationships between forms of material damage, visual indication of damage, mechanical compliance of the material and resonant modes in the conductance signature of PZT bonded to a concrete substrate are investigated. The variation in surface strains for incremental levels of loading is monitored using Digital Image Correlation (DIC) and compared with the conductance plot of the PZT. Root mean square deviation (RMSD) of the EM conductance close to the resonant peak is used as a damage index and variation in RMSD at different damage states is presented.

**Experimental Program**

Experiments were performed using 150 mm concrete cubes. Six cubes were cast and cured for 90 days before testing. The properties of the cube is given in table1. The three cubes were tested to failure to determine the compressive strength of the concrete.

Table 1 Properties of materials				
Type	Average Failure stress (Mpa)	Young's Modulus (GPa)	Density (ρ) (kg/m <sup>3</sup> )	Poisons ratio (ν)
Concrete cube	52	36	2300	0.2
Epoxy	-	2	1400	0.36

The cubes were bonded with PZT patches exactly at the center of the side face of the cube using two component epoxy. A 20mm x 20mm PZT patch, which was 1mm in thickness, was used for the experimental study. The front faces of the cubes were smoothed and a sprayed-on speckle pattern was created for measurement of surface displacements using the full-field optical technique known as digital image correlation (shown in Figure 1a). The baseline signatures of the PZT when attached to the substrate are taken.

In a typical impedance measurement, the frequency was varied between 1 kHz and 0.5 MHz at an applied voltage of 1V and data was collected at 800 discrete frequencies.

Average of five measurements was collected. Impedance data was collected from the PZT patch in the free-state before attaching the PZT to the concrete cube. The baseline EM conductance signature and image were taken prior to the start of loading. Cubes were subjected to cyclic compressive loading of increasing magnitude where the load amplitude was increased in increments of 10% of the average compressive strength in every cycle. The loading procedure consisted of alternate loading and unloading cycles as shown in Figure 1b. During the loading, the conductance signatures and the image for DIC were recorded on top of the load cycle and after unloading.

**EM Impedance of PZT**

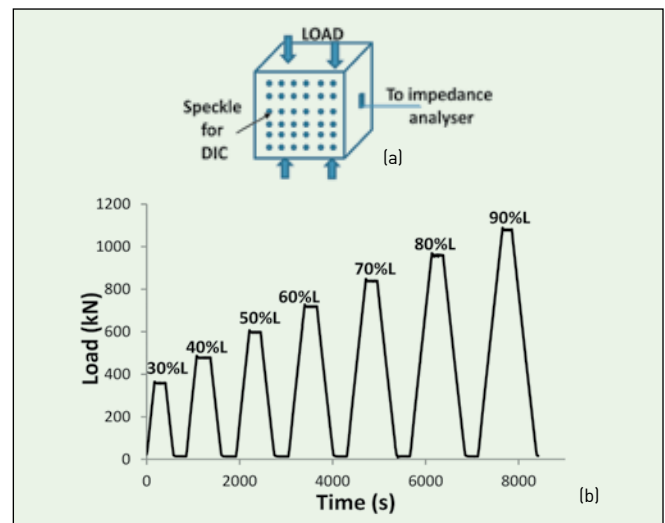


Fig. 1: (a) Experimental set up (b) Applied loading history

In a PZT material, the application of an electrical field results in mechanical strain in the material due to the coupled electro-mechanical constitutive relations. For a PZT patch attached to a substrate subjected to an applied electrical input, the motion of the interface subjected to continuity conditions is governed by the combined mechanical impedance of the structure and the PZT. The constrained motion in turn produces a change in the measured electrical impedance. The first systematic attempt to derive the electrical impedance of the PZT which is mechanically connected to a structure using a 1D idealization of the system was developed by Liang et al. (1994). Subsequent improvements in modelling the PZT response have included the effective 1-D model of the PZT and varying levels of idealization of the structural impedance [Bhalla et al. (2004), Xu (2002), Yang et al (2005)]. Most of the available analytical solutions are applicable for 1 or 2-D idealizations of the PZT, substrate or both. Typically the electrical impedance of the PZT patch for a given electrical input at a frequency can be represented as

$$\tilde{Y} = \tilde{Y}(Z_A, Z_S, \omega, l_i, E) \dots\dots\dots(1)$$

where  $Z_A$  and  $Z_C$  are the mechanical impedance of the PZT

and substrate respectively.  $l_i$  represent the dimensions of patch and  $E$  is the electric field applied for actuation. The functional form of Equation (1) is not readily available for the test configuration used in this study.

The conductance, which is the real part of admittance of the free PZT and the PZT bonded to the 150 mm concrete cube are shown in Figure 2. It can be seen that resonance peaks associated with the free vibration of the PZT can also be identified in the response of the PZT attached to the concrete cube. Only three prominent peaks are identified in the conductance spectrum of the bonded PZT. Peaks 1 and 2 in the conductance spectrum of the bonded PZT correspond with modes 1 and 3 respectively of the PZT. The third peak in the conductance response of the bonded PZT has contributions from closely spaced modes 5 and 6 of the PZT. There are several prominent changes associated with the frequency of the resonant modes and the relative magnitude of the resonant peaks. There is a noticeable decrease in values of conductance, an increasing baseline trend which increases the magnitude of conductance with increasing frequency and a change in the relative magnitudes of the resonant peaks in the bonded state. There is also a significant broadening of the resonance peaks compared with the free-state. The resonance peaks shift to higher frequencies, with a larger frequency shift in lower modes.

The resistance to the motion of the PZT by the substrate is reflected in the overall decrease in the value of conductance. While the conductance of the free PZT is essentially zero between resonant peaks, the conductance is non-zero between the resonant peaks for the bonded PZT. The resistance to the motion of a point located on the surface of the cube, given by the driving point impedance, influences the motion of the bonded PZT. The frequency dependency of the substrate driving point impedance is reflected in the relative shifts in the amplitudes and the general increasing trend in the background of the measured conductance. The influence of the substrate can also be identified with the overall increase in the frequency and broadening of the resonant peaks.

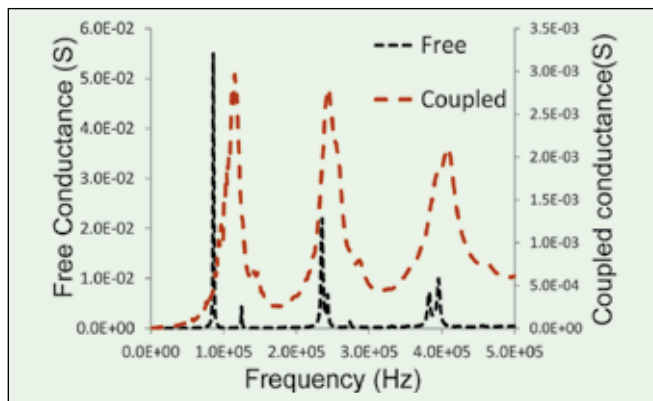


Fig. 2: Conductance spectrum of PZT in the free condition and coupled with a 150 mm concrete cube.

### Analysis of results

From the results of the numerical analysis, the second peak in the EM conductance response of the bonded PZT was selected for evaluating the influence of load-induced damage. The conductance signatures at the second peak of the bonded PZT response after unloading from different load levels are shown in figures 3. The second peak is centered on 255 kHz. The response between 245 and 265 kHz is plotted in the figures. Contours of horizontal strain at distinct loading obtained from the DIC technique are shown in figure 4. It can be clearly identified from the plot that the unloading signature at 40%u shows a left ward shift. This is due to the incipient damage produced in the concrete. Horizontal strain contour shows an increase in strain levels (figure 4). As the load level increases, the resonance peak in the conductance signature shows a consistent leftward shift. Comparing with the measured DIC response, there is no visible sign of distress or cracking up to 70% of strength, while some signs of localization are evident at 60% of peak. Localization of damage into a crack occurs at 70% of strength. Significant changes in the resonant peak associated with the localization are observed. After localization, significant changes are observed in the shape of the resonant peak. At 90% of the compressive strength, the peak showed a significant decrease in amplitude and a flattening of the peak. The flattening of the peak is associated with the formation of a major crack on the surface. The conductance signatures associated with the resonant peak has a very good agreement with the indication of damage obtained from surface strain measurements. Further, changes in EM conductance are observed before any visible sign of distress.

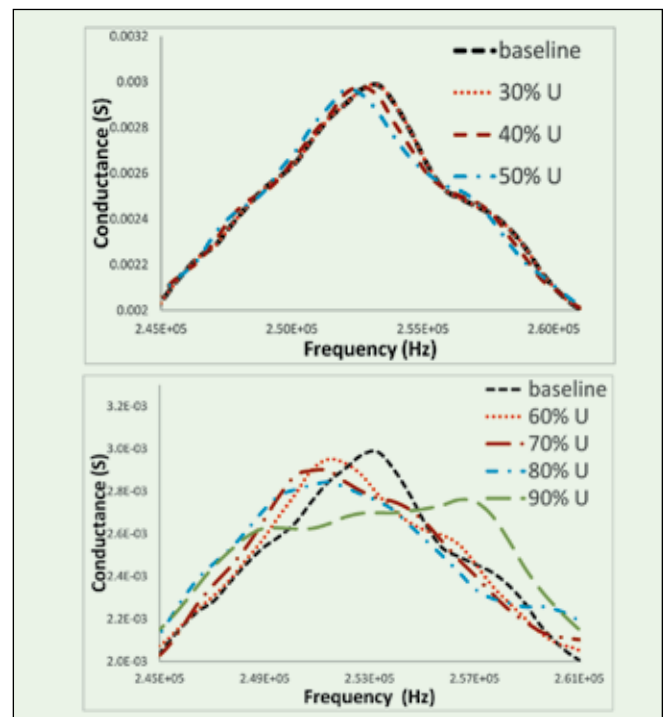


Fig. 3: Electrical conductance signatures: a. 30%-50% of strength b. 60%-90% of strength

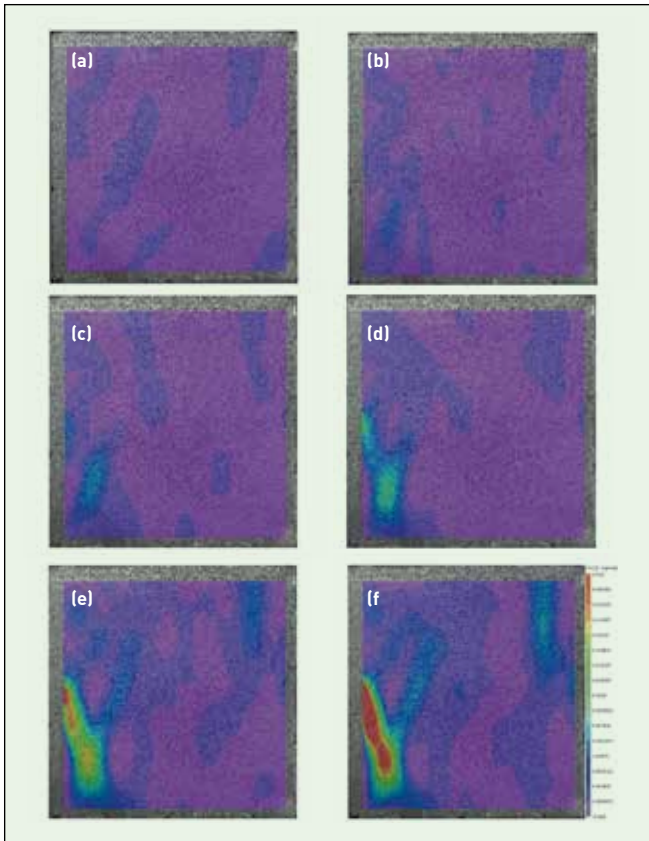


Fig. 4: Contours of horizontal strain ( $\epsilon_{xx}$ ) obtained using digital image correlation (a) at 40%; (b) at 50%; (c) at 60%; (d) at 70%; (e) at 80%; and (f) at 90% of Strength.

The root-mean-square deviation (RMSD) is used to measure the differences between values of baseline measurement of conductance signature at the second resonant peak and the corresponding signatures at different load levels. The RMSD for the frequency range 245 kHz-260 kHz with respect to the baseline measurement were calculated using equation 2, where  $x_i$  and  $y_i$  are the signatures obtained from the PZT transducer bonded to the structure before and after damage (or loading). The scatter in the results obtained from all the specimens is also plotted in the figure. It can be seen that despite the scatter, there is an increasing trend of RMSD with each level of loading as shown in the figure. The variation in the average vertical strains recorded at the top and bottom of the load cycles obtained from DIC measurements are also plotted in Figure 5b. It can be seen that the level of damage assessed using the RMSD variation of the second resonant peak compares well with the evolution of plastic strain and increase in mechanical compliance. There is an exponential increase in the evolution of plastic strain with loading. Plastic strain is an indicator of level of damage in the material. This corresponds with the observed trend in the RMSD measure with loading.

$$RMSD = \sqrt{\frac{\sum_{i=1}^N (y_i - x_i)^2}{\sum_{i=1}^N x_i^2}} \dots\dots\dots [2]$$

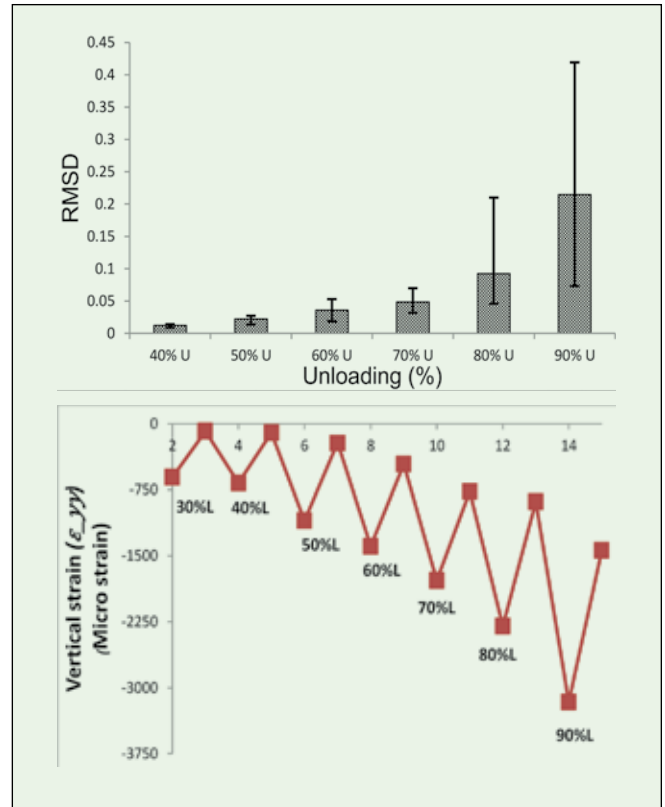


Fig. 5: RMSD of the second resonance peak b. Average vertical strain ( $\epsilon_{yy}$ ) obtained From DIC

**Conclusions**

Potential of using EM impedance measurements of surface mounted PZT patches for structural health monitoring of concrete structures is presented in the paper. It is shown that there are changes in resonant behavior of the EM conductance response of the PZT bonded to a concrete substrate with increasing damage. The PZT sensor detects incipient damage significantly earlier than the appearance of visible signs of damage. There is an amplitude reduction and frequency shift of the PZT resonance peak with an increase in damage in the concrete substrate. At higher damage levels, there is flattening of the resonant peak associated with localization and formation of a major crack.

**References**

1. Ayres, J.W., Lalande, F., Chaudhry, Z., and Rogers, C.A., 1998. Qualitative impedance-based health monitoring of civil infrastructures. *Smart Materials and Structures*, 7(5):599-605.
2. Bhalla, S., and Soh, C.K., 2004. Structural Health Monitoring by Piezo-Impedance Transducers. I: Modeling. *Journal of Aerospace Engineering*, 17(4):154-165.
3. Chaudhry, Z., Joseph, T., Sun, F., and Rogers, C.A., 1995. Local-Area Health Monitoring of Aircraft via Piezoelectric Actuator/Sensor Patches. *Proceedings, SPIE North American Conference on Smart Structures and Materials*, 2443:268-276.
4. Giurgiutiu, V., and Rogers, C. A., 1997. Electro-mechanical (E/M) impedance method for structural health monitoring and non-destructive evaluation. *International Workshop on Structural Health Monitoring*, Stanford University, CA, September 18-20:434-444.

5. Giurgiutiu, V., and Zagrai, A.N., 2000. Characterization of Piezoelectric Wafer Active Sensors. *Journal of Intelligent Material Systems and Structures*, 11(12):959-976.
6. Giurgiutiu, V., Reynolds, A., and Rogers, C.A., 1999. Experimental Investigation of E/M Impedance Health Monitoring for Spot-Welded Structural Joints. *Journal of Intelligent Material Systems and Structures*, 10(10):802- 812.
7. Giurgiutiu, V., Zagrai, A.N., and Bao, J.J., 2002. Piezoelectric Wafer Embedded Active Sensors for Aging Aircraft Structural Health Monitoring. *Structural Health Monitoring*, 1(1): 41-61.
8. Giurgiutiu, V., Zagrai, A.N., and Bao, J.J., 2004. Damage Identification in Aging Aircraft Structures with Piezoelectric Wafer Active Sensors. *Journal of Intelligent Material Systems and Structures*, 15(9):673-687.
9. Liang, C., Sun, F.P., and Rogers, C.A., 1994. An Impedance Method for Dynamic Analysis of Active Material Systems. *Journal of Vibration and Acoustics*, 116(1):120-128.
10. Lim, Y.Y., Bhalla, S., and Soh, C.K., 2006. Structural identification and damage diagnosis using self-sensing piezo-impedance transducers. *Smart Materials and Structures*, 15(4):987-995.
11. Park, G., Cudney, H., and Inman, D., 2000. Impedance-Based Health Monitoring of Civil Structural Components. *Journal of Infrastructure Systems*, 6(4):153-160.
12. Peairs, D.M., Park, G., and Inman, D.J., 2004. Improving Accessibility of the Impedance-based Structural Health Monitoring Method. *Journal of Intelligent Material Systems and Structures*, 15(2):129-139.
13. Sun, F.P., Chaudhry, Z., Liang, C., and Rogers, C.A., 1995. Truss Structure Integrity Identification Using PZT Sensor-Actuator. *Journal of Intelligent Material Systems and Structures*, 6(1):134-139.
14. Tseng, K.K., and Wang, L., 2004. Smart piezoelectric transducers for in situ health monitoring of concrete. *Smart Materials and Structures*, 17(5):1017-1024.
15. Wang, D., Song, H., and Zhu, H., 2013. Numerical and experimental studies on damage detection of a concrete beam based on PZT admittances and correlation coefficient. *Construction and Building Materials*, 49:564-574.
16. Xu, Y.G., and Liu, G.R., 2002. A Modified Electro-Mechanical Impedance Model of Piezoelectric Actuator- Sensors for Debonding Detection of Composite Patches. *Journal of Intelligent Material Systems and Structures*, 13(6):389-396.
17. Yang, Y., Xu, J., and Soh, C.K., 2005. Generic Impedance-Based Model for Structure-Piezoceramic Interacting System. *Journal of Aerospace Engineering*, 18(2):93-101.
18. Zagrai, A.N., and Giurgiutiu, V., 2001. Electro-Mechanical Impedance Method for Crack Detection in Thin Plates. *Journal of Intelligent Material Systems and Structures*, 12(10):709-718.



### Arun Narayanan

Arun Narayanan is a research scholar in Department of civil engineering at Indian institute of technology Hyderabad, India. His areas of interest are Sensor Development for Structural Health Monitoring; Structural dynamics, Non- destructive Evaluation.



### K. V. L. Subramaniam

Prof. K. V. L. Subramaniam is currently the Dean (Planning and Development) and a Professor in the Department of Civil Engineering at Indian Institute of Technology Hyderabad (IITH). Prior to joining IITH, he was a Professor and Catell Fellow in Department of Civil Engineering at the Grove School of Engineering, the City College of New York (CCNY). Dr. Subramaniam obtained a B.Tech. in Civil Engineering from IIT Delhi and Ph.D. in Structural Engineering and Materials from Northwestern University, Evanston. After graduation, Dr. Subramaniam worked as a Research Associate at the NSF Center for Advanced Cement Based Materials. Dr. Subramaniam's research interests include Fracture and Fatigue of cementitious materials, FRP-based Structural Strengthening, Fly ash based binders, Geopolymers and Non-destructive testing and evaluation techniques for concrete structures.