

# Ab initio study of Fermi surface and dynamical properties of $\text{Ni}_2\text{XAl}$ (X=Ti, V, Zr, Nb, Hf and Ta)

P. V. Sreenivasa Reddy, V. Kanchana\*

Department of Physics, Indian Institute of Technology Hyderabad, Ordnance Factory Estate, Yeddumailaram-502 205, Andhra Pradesh, India.

---

## Abstract

A detailed study on the pressure and temperature effects on ternary Ni-based inter-metallic compounds  $\text{Ni}_2\text{XAl}$  (X=Ti, V, Zr, Nb, Hf and Ta) have been carried out using density functional theory. The calculated ground state properties are in good agreement with experiments for all the investigated compounds. The band structures and Fermi surface topology is found to be quite similar for all the compounds except for  $\text{Ni}_2\text{NbAl}$ , where we find an extra band to cross the Fermi level under compression resulting in a new electron pocket at X-point.  $\text{Ni}_2\text{NbAl}$  is found to be a superconductor with superconducting transition temperature of 3.1 K which agrees quite well with the experimental value and the calculated  $T_c$  is found to vary non-monotonically under pressure. From the calculated phonon dispersion relation, we find all the investigated Ni-based Heusler compounds to be dynamically stable, until high pressure. The ductile nature of these compounds is confirmed from the calculated Cauchy's pressure, Pugh's ratio and Poisson's ratio. In addition, the thermodynamic properties show  $\text{Ni}_2\text{TiAl}$  to have lower specific heat and entropy but higher internal energy and free energy among all the investigated compounds.

**Keywords:** Transition metal alloys and compounds, Electronic band structure, Phonons, Thermodynamic properties, Electron-phonon interactions.

---

## 1. Introduction

Ternary intermetallic Heusler alloys  $\text{Ni}_2\text{XAl}$  (X=Ti, Zr, Hf, V, Nb, and Ta) with chemical formula  $\text{A}_2\text{YZ}$  crystallize in cubic  $L2_1$ - structure, where A and Y are the transition metals and Z is a non-magnetic element [1]. Though the Heusler compounds are well known for their ferromagnetic properties, it is interesting to note the existence of paramagnetic compounds, one among them is the above mentioned series  $\text{Ni}_2\text{XAl}$  [2].  $\text{Ni}_2\text{TiAl}$  and many other Ni-based compounds have been explored from various perspective, ever since it was found that the high temperature creep resistance of NiAl could be improved by Ti addition [3], which stabilized the compounds in the Heusler type structure. The structural properties of  $\text{Ni}_2\text{TiAl}$  was further studied experimentally by Taylor and Floyd [4], using X-rays and electron spectroscopy and Umakoshi et al. [5] further confirmed  $\text{Ni}_2\text{TiAl}$  to have small lattice mismatch with B2 phase and found the same to possess good stability. This se-

ries attracted further interest and a complete phase diagram of  $\text{Ni}_2\text{TAl}$  (T = Zr, Nb and Ta) was obtained by Raman and Schubert [6]. Theoretical insight on the above mentioned series was also provided by Lin and Freeman [2] further substantiating the stability of  $L2_1$  structure of  $\text{Ni}_2\text{XAl}$  (X = Zr, Nb and Ta). Further, Da Rocha et al. [7] have reported the specific heat and electronic structure of the above mentioned series. Heusler alloys ever remain a perennial resource of compounds with plethora of studies available explaining the transport, electrical conductivity, magnetic and many other properties owned by them [8, 9, 10]. It is further interesting to note that  $\text{Ni}_2\text{NbAl}$ , one among  $\text{Ni}_2\text{XAl}$  being studied, is reported to be a superconductor experimentally with the transition temperature around 2.1 K [11]. Though the binary Ni-based intermetallic compounds were primarily known for high temperature applications [12, 13, 14, 15, 16], ternary Ni-intermetallics based on the  $L2_1$  structure are found to possess various properties such as superconductivity, magnetism, spintronics [3, 17, 18, 19, 20, 21, 22, 23, 24] etc., and deserves further investigation which form the main goal of the present work. Our main objective is to explore

---

\*Corresponding author

Email address: kanchana@iith.ac.in (V. Kanchana)

this series for wide range of applications, for which the electronic structure and the other related properties have to be studied, which is taken up in the present work. Though electronic structures are available for few of these compounds, we focus on the Fermi surface topology, dynamical stability, mechanical and thermodynamics properties of these compounds through computer simulations. In addition, we have also studied the effect of pressure on the Fermi surface and thermodynamic properties, as the Fermi surface topology change can be related to the anomalies observed in the physical properties [25, 26, 27, 28, 29, 30]. Recently it was shown that the Fermi surface topology change can be used to predict the trends in the superconducting transition temperature ( $T_c$ ) [25, 26]. As  $Ni_2NbAl$  is a superconductor, we have performed the Fermi surface studies under pressure to predict the trend in the variation of  $T_c$  under pressure.

The organization of the paper is as follows. Section 2 given the computational details of the present work. The results and discussions are presented in section 3 which is again divided into five subsections. Ground state properties and electronic structure properties are given in the first subsection. In this subsection we discuss the band structure, density of states (DOS), Fermi surfaces (FS) of all the compounds at ambient as well as under compression. Elastic constants of all the compounds are calculated using theoretical lattice constant and are discussed in second subsection. Vibrational properties are discussed in third subsection. The superconductivity of  $Ni_2NbAl$  is discussed in the fourth subsection. We have discussed the thermodynamic properties in the last subsection. Finally conclusions are presented in section 4.

## 2. Methodology

Two distinct density functional calculations have been used in the present work to calculate the electronic structure and vibrational properties. The Full-Potential Linearized Augmented Plane Wave (FP-LAPW) method as implemented in the WIEN2k [31, 32] code is used to calculate the electronic structure and Fermi surface properties, and PBE-GGA [33] (Perdew-Burke-Ernzerhof parametrization of the Generalized Gradient Approximation) approximation has been used for the exchange correlation potential. Throughout the calculations, the  $R_{MT}$  (radius of muffin tin spheres) value for each atom was fixed as 1.78 a.u for Ni atom, 1.78 a.u for X (X=Ti, V, Zr, Nb, Hf and Ta) atom and 1.67 a.u for Al atom. For the energy convergence, the criterion  $R_{MT} * K_{max} = 9$  was used, where  $K_{max}$  is the plane wave cut-off. The potential and

charge density were Fourier expanded up to  $G_{max} = 12 \text{ a.u}^{-1}$ . The valence states included in the calculations are Ni ( $3d^8, 4s^2$ ), Al ( $3s^2, 3p^1$ ), Ti ( $3d^2, 4s^2$ ), V ( $3d^3, 4s^2$ ), Zr ( $4d^2, 5s^2$ ), Nb ( $4d^4, 5s^1$ ), Hf ( $4f^{14}, 5d^2, 6s^2$ ), Ta ( $4f^{14}, 5d^3, 6s^2$ ) and the remaining orbitals are treated as core states. All the electronic properties like band structure, density of states and Fermi surface are calculated with  $44 \times 44 \times 44$  k-mesh in the Monkhorst-Pack [34] scheme which gives 2168  $k$ -points in the irreducible part of the Brillouin Zone (BZ) to ensure accurate determination of the Fermi level. For the Brillouin zone integration we have used the tetrahedron method [35]. Birch-Murnaghan [36] equation of state was used to fit the total energies as a function of primitive cell volume to obtain the bulk modulus and the equilibrium lattice parameter for all the investigated compounds.

The thermodynamic properties are calculated using the Quasi-Harmonic Approximation as implemented in the QUANTUM ESPRESSO [37] simulation package with temperature ranging from 0 to 500 K. All the phonon calculations are performed using the plane wave self-consistent field (Pwscf) program based on ultrasoft pseudopotential [38]. These thermodynamic calculations are carried out with the kinetic energy cut-off of 42 Ry (ecutwfc) and the Gaussian broadening of 0.02 Ry (dgauss) and a  $4 \times 4 \times 4$  uniform grid of  $q$ -points are used for all the compounds. The exchange-correlation functional of PBE within the GGA is used for the calculations. We have calculated the electron-phonon coupling constant  $\lambda_{ep}$  by using Eliashberg function for  $Ni_2NbAl$  and with this  $\lambda_{ep}$  the  $T_c$  is calculated using the Allen-Dynes formula [39]. The temperature dependent bulk modulus and linear expansion coefficient for all the compounds are also calculated using GIBBS2 program [40].

## 3. Results and Discussions

### 3.1. Ground state and Electronic structure (Band structure, Density of states and Fermi surface) properties

The basic ground state properties are calculated using the Birch-Murnaghan equation of state and the results are reported in Table I, along with the available experimental results. From the calculated values, we see that the maximum error in the lattice parameter is 0.47% for  $Ni_2TiAl$  and the minimum error is 0.03% for  $Ni_2VAl$ .

Electronic structure of all the investigated compounds are studied at ambient as well as under compression. The semi-relativistic band structure of these compounds

Table 1: The calculated theoretical lattice parameter ( $a_{the}$ ) compared with the experimental lattice parameter ( $a_{exp}$ ), bulk modulus ( $B$ ), density of states at the Fermi level ( $N(E_F)$ ) (states/eV/f.u.) and Sommerfeld coefficient ( $\gamma$ ) (mJ/mol K<sup>2</sup>) of Ni<sub>2</sub>XAl (X=Ti, Zr, Hf, V, Nb, Ta).

Parameters	Ti	Zr	Hf	V	Nb	Ta
$a_{the}$ (Å)	5.90	6.13	6.10	5.80	5.99	5.98
$a_{exp}$ (Å)	5.87 [2]	6.12 [2]	6.08 [2]	5.80 [7]	5.97 [2]	5.96 [7]
$B$ (GPa)	164	151	158	181	181	191
DOS $N(E_F)$	3.50	3.25	2.81	3.51	2.27	2.13
$\gamma$	8.25	7.65	6.63	8.27	5.36	5.02

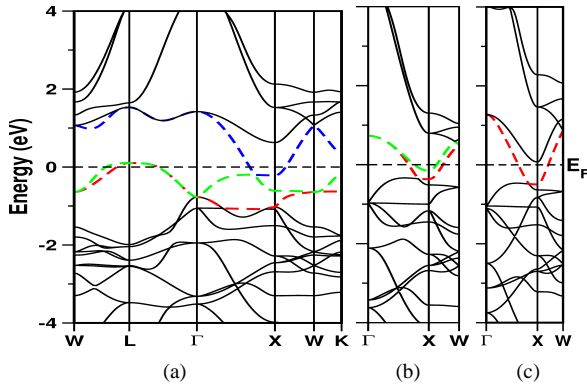


Figure 1: (color online) Band structure at ambient condition (at experimental volume) for (a) Ni<sub>2</sub>TiAl (same for Ni<sub>2</sub>ZrAl and Ni<sub>2</sub>HfAl)(b) Ni<sub>2</sub>VAl (c) Ni<sub>2</sub>NbAl (same for Ni<sub>2</sub>TaAl).

are shown in Fig.1. We have also checked the effect of Hubbard 'U' and found no appreciable changes in the band structure as these are metallic systems and are not correlated. This is consistent with the recent studies on Heusler based compounds where the authors also concluded the same [41]. The overall profile of all these Ni<sub>2</sub>XAl compounds are the same, whereas the number of bands crossing the  $E_F$  is not the same for all the compounds. For Ni<sub>2</sub>TiAl, Ni<sub>2</sub>ZrAl and Ni<sub>2</sub>HfAl three bands cross the  $E_F$ , two of them crossing at the  $L$ -point from valence band to conduction band (Here the conduction bands refer to the bands above the Fermi level and they are primarily  $X$ -derived states) and the third band crosses the  $E_F$  from conduction band to valence band at  $X$ -point (band structure of Ni<sub>2</sub>TiAl is shown in Fig.1). For Ni<sub>2</sub>VAl, we observe two bands to cross the Fermi level at  $X$ -point from conduction band to valence band. For Ni<sub>2</sub>NbAl and Ni<sub>2</sub>TaAl compounds, we find only one band to cross the  $E_F$  from conduction band to valence band at  $X$ -point at ambient condition.

To analyze in detail, we have also calculated the density of states for all these compounds as shown in Fig.2 and it is evident that the contribution at  $E_F$  is mainly

dominated by Ni- $d_{eg}$  states with an admixture of  $X$ - $d_{t2g}$  and Al- $p$  states. The states at nearly -6 eV is mainly derived from the Al- $s$  states. For all the compounds the bonding and the anti-bonding regions are well separated from the non-bonding region and our calculations agree well with the earlier studies [2]. As we move to compounds containing V-B elements we could see the states to shift below  $E_F$  due to band filling and is clearly evident from Fig.2. Apart from this, our calculated density of states at the Fermi level show a decreasing trend as we move from top to bottom of the periodic table.

In addition, the Fermi surfaces of all the investigated compounds at ambient conditions are shown in Fig.3, for the corresponding band which crosses the  $E_F$  as shown in Fig.1. We observe the Fermi surface topology to be quite similar for Ni<sub>2</sub>TiAl, Ni<sub>2</sub>ZrAl and Ni<sub>2</sub>HfAl (FS for Ni<sub>2</sub>ZrAl and Ni<sub>2</sub>HfAl compounds are not displayed) indicating the dominating nature of the Ni- $d$  states with small contribution from  $X$ - $d$  states at  $E_F$ . For Ni<sub>2</sub>TiAl, Ni<sub>2</sub>ZrAl and Ni<sub>2</sub>HfAl compounds which contain IV-B elements we find the Fermi surface to be of electron character at  $X$ -point and hole character at  $L$ -point respectively and is also evident from the band structure plot from Fig.1, whereas in Ni<sub>2</sub>VAl, Ni<sub>2</sub>NbAl and Ni<sub>2</sub>TaAl compounds which contain V-B elements, we find the band to cross only at  $X$ -point resulting in the electron pocket at the same point. From Fig.3(d,e) it is evident that Ni<sub>2</sub>VAl has two FS as a result of two bands crossing the  $E_F$  (see Fig.1(b)) and the remaining two compounds Ni<sub>2</sub>NbAl, Ni<sub>2</sub>TaAl have only one FS, due to a single band crossing the  $E_F$  (see Fig.1(c)).

We have also studied the band structure and Fermi surface under compression. For all these compounds under study, we observe the FS topology to remain unaltered under compression with slight change in the size of the electron or hole pocket, which might be due to the bands crossing the Fermi level being less dispersive at the high symmetry points. Under compression an interesting feature to note is that, we find an additional electron pocket to appear in Ni<sub>2</sub>NbAl at around  $V/V_0=0.93$

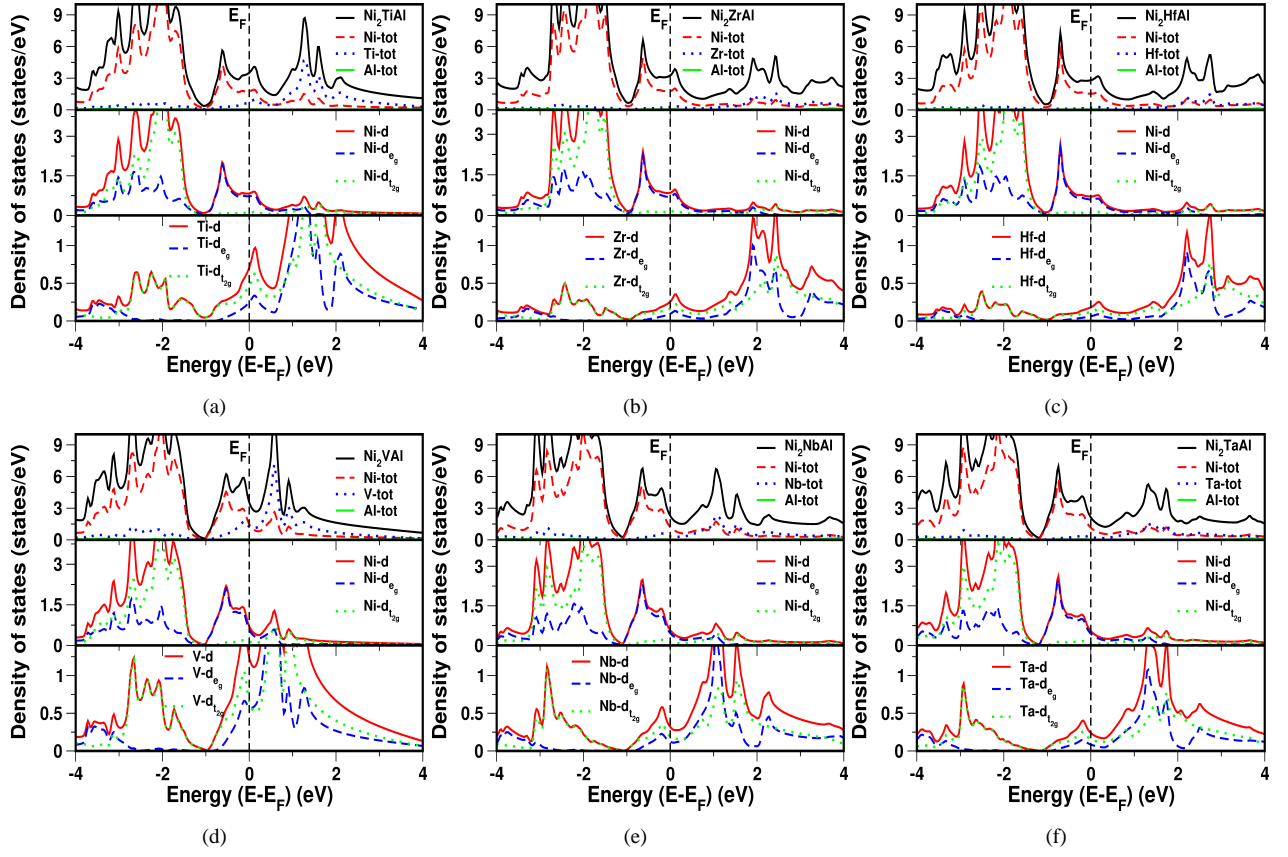


Figure 2: (color online) Density of states at ambient (at experimental volume) for (a)  $\text{Ni}_2\text{TiAl}$  (b)  $\text{Ni}_2\text{ZrAl}$  (c)  $\text{Ni}_2\text{HfAl}$  (d)  $\text{Ni}_2\text{VAl}$  (e)  $\text{Ni}_2\text{NbAl}$  (f)  $\text{Ni}_2\text{TaAl}$  compounds.

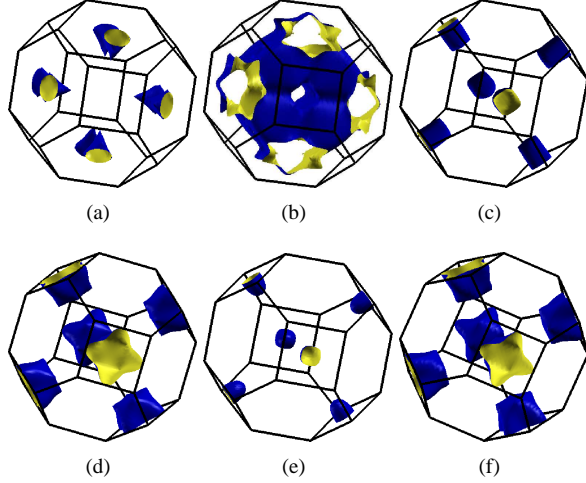


Figure 3: (color online) Fermi surfaces of (a,b,c)  $\text{Ni}_2\text{TiAl}$  (same for  $\text{Ni}_2\text{ZrAl}$  and  $\text{Ni}_2\text{HfAl}$ ), (d,e)  $\text{Ni}_2\text{VAl}$ , (f)  $\text{Ni}_2\text{NbAl}$  (same for  $\text{Ni}_2\text{TaAl}$ ) at experimental volume.

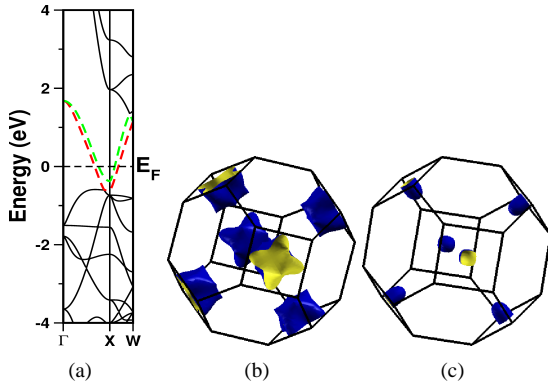


Figure 4: (color online) (a) Band structure under compression (at  $V/V_0 = 0.93$ , where  $V_0$  is the experimental volume) for  $\text{Ni}_2\text{NbAl}$  compound and the corresponding FS (b,c) at the same compression.

(pressure of 17 GPa) which is due to the band dropping down the  $E_F$  at the  $X$ -point and is shown in Fig.4 (a) and the corresponding Fermi surfaces are shown in the Fig.4 (b,c).

### 3.2. Elastic constants

To account for the mechanical stability of all the investigated compounds we have calculated the elastic constants. All the above mentioned compounds crystallize in the cubic structure and have three non-zero elastic constants  $C_{11}$ ,  $C_{12}$ ,  $C_{44}$ . The calculated single crystal elastic constants at equilibrium volume are given in Table II for all the compounds. The calculated elastic constants of all the compounds satisfy the Born mechanical stability criteria [42] i.e.  $C_{11} > 0$ ,  $C_{44} > 0$ ,  $C_{11} > C_{12}$ , and  $C_{11} + 2C_{12} > 0$ , which indicate these compounds to be mechanically stable at ambient condition. From the single crystal elastic constants, we have calculated the Young's modulus  $E$ , Voigt-Reuss-Hill modulus  $G_H$  [43], Poisson's ratio  $\sigma$ , Anisotropy factor  $A$  and are reported in Table II. The relations between  $C_{11}$ ,  $C_{12}$ ,  $C_{44}$  and the above mentioned parameters can be found elsewhere [44, 45, 46, 47].

Debye temperature ( $\Theta_D$ ) is one of the most important parameter and it determines the thermal characteristics of the materials. The Debye temperature can be obtained from the mean sound velocity, which gives the explicit information about lattice vibration and can be computed directly from the given relation.

$$\Theta_D = \frac{h}{k} \left[ \frac{3n}{4\pi} \left( \frac{\rho N_A}{M} \right) \right]^{1/3} v_m \quad (1)$$

where ' $h$ ' is the Planck's constant, ' $k$ ' is the Boltzmann's constant, ' $N_A$ ' is the Avogadro's number, ' $\rho$ ' is the density, ' $M$ ' is the molecular weight, ' $n$ ' is the number of atoms in the unit cell, and ' $v_m$ ' is the mean sound velocity, which can be calculated by using the following relation.

$$v_m = \left[ \frac{1}{3} \left( \frac{2}{v_l^3} + \frac{1}{v_t^3} \right) \right]^{-1/3} \quad (2)$$

where ' $v_l$ ' and ' $v_t$ ' are the longitudinal and transverse sound velocities obtained using the shear modulus  $G_H$  and the bulk modulus  $B$ .

$$v_l = \sqrt{\frac{(B + \frac{4}{3}G_H)}{\rho}} \quad (3)$$

$$v_t = \sqrt{\frac{G_H}{\rho}} \quad (4)$$

Table 2: Calculated elastic constants and derived quantities for Ni<sub>2</sub>XAl (X=Ti, Zr, Hf, V, Nb, Ta) at the theoretical lattice constant.  $v_l$ ,  $v_t$ ,  $v_m$  are the longitudinal, transverse and mean sound velocities. (CP = Cauchy's pressure)

Parameters	Ti	Zr	Hf	V	Nb	Ta
$C_{11}$ (GPa)	223	217	211	200	212	229
$C_{12}$ (GPa)	135	119	132	171	167	172
$C_{44}$ (GPa)	104	81	90	109	98	109
$E$ (GPa)	193	174	171	138	150	172
$A$	2.36	1.65	2.27	7.69	4.37	3.89
CP	30.18	37.41	41.64	62.33	68.26	63.01
Pugh's ratio	0.45	0.44	0.41	0.28	0.30	0.33
$\sigma$	0.30	0.31	0.32	0.37	0.36	0.35
$G_H$ (GPa)	74.00	66.37	64.85	50.43	54.99	63.79
$v_l$ (km/s)	13.00	11.88	10.17	12.22	11.81	10.48
$v_t$ (km/s)	6.89	6.25	5.24	5.51	5.48	5.04
$v_m$ (km/s)	7.71	6.99	5.86	6.21	6.17	5.66
$\Theta_D$ (K)	617.89	539.17	454.73	506.42	487.11	446.99

The calculated values for all the above defined parameters are given in Table II. From Table II, it is seen that Ni<sub>2</sub>TiAl has higher Young's modulus in comparison with other compounds which might imply Ni<sub>2</sub>TiAl to be stiffer among the other compounds studied. The elastic anisotropy gives the possibility of inducing micro cracks in the materials [44] and the calculated value of the elastic anisotropy of all the studied compounds are given in the Table II.

The Cauchy's pressure ( $C_{12} - C_{44}$ ) can be used to comment on the ductile or brittle nature of the compounds. Here Cauchy's pressure for all the compounds is positive indicating the ductile nature. Pugh's ratio ( $\frac{G_H}{B}$ ) [48] is another index for explaining the ductile and brittle nature of the compounds. Larger and smaller values of Pugh's ratio indicate the brittle and ductile nature of the material respectively. The critical number which separates the ductile and brittle nature was reported to be 0.57. This series of compounds have the Pugh's ratio values lesser than this critical number indicating the ductile nature. The Poisson's [49] ratio indicate the stability of the crystal against shear and takes the values in between -1 to 0.5, where -1 and 0.5 serve as lower and upper bounds respectively. The lower bound is the one where the materials does not change its shape and the upper bound is where the volume remains unchanged. These compounds have the Poisson's ratio values closer to the upper limit indicating the stiffness of these compounds. From the reported values as shown in Table II, we could see the Poisson's ratio to be higher for the compounds having IV-B group elements and lower for compounds which have V-B group elements. The De-

bye temperature which is used to estimate the thermal properties of material is also calculated with the help of mean sound velocity. From Table 2, we find Debye temperature and mean sound velocities to decrease as we move from top to bottom in the periodic table and higher  $\theta_D$  values indicate higher thermal conductivity associated with these compounds.

### 3.3. Vibrational properties

We have also calculated the phonon dispersion along the high symmetry directions of the Brillouin zone to find the dynamical stability of these compounds at ambient as well as under compression along with the phonon density of states and are shown in Fig.5. The unit cell of Ni<sub>2</sub>XAl contains four atoms, which gives rise to 12 phonon branches in all, out of which three are acoustical and nine are optical modes. However this number is reduced in different directions due to degeneracy. The absence of imaginary frequency in all high symmetry direction for all the investigated compounds confirm the dynamical stability at ambient as well as under compression. The same stability was not found for other Ni-based Heusler alloys, Ni<sub>2</sub>MnAl and Ni<sub>2</sub>MnGa reported earlier due to the presence of the imaginary frequencies [50, 22]. We find all the phonon modes to harden under compression as evident from the Fig.6 and is further confirmed from the mode Grüneisen parameters as reported in Table III, which is a most important physical quantity, relating the volume variation with the phonon frequencies and is defined as

$$\gamma_i = \partial(\ln\omega_i)/\partial(\ln V) \quad (5)$$

Table 3: Grüneisen mode parameter at Gamma point for Ni<sub>2</sub>XAl (X=Ti, Zr, Hf, V, Nb, Ta).

Mode	Ti	Zr	Hf	V	Nb	Ta
T <sub>2g</sub>	2.16	2.22	2.02	2.14	2.55	2.41
T <sub>1u</sub>	1.48	1.46	1.41	2.08	1.97	1.74
T <sub>1u</sub>	1.43	1.46	1.55	2.08	1.59	1.62

where  $\omega_i$  is the frequency of the specific mode and  $V$  is the volume. These values again confirm the dynamical stability of these studied compounds until high pressure, which is seen from the obtained positive slope for all the modes. Again the hardening of phonon modes are more pronounced for the compounds which have V-B group elements than the compounds having IV-B group elements. We observed that for all the compounds maximum contribution at higher and lower frequency regions is mainly from Al, Ni atoms respectively. In the middle frequency region for Ni<sub>2</sub>XAl (X = Ti, V, Zr, Nb) compounds the maximum contribution is from X atom and in the case of Ni<sub>2</sub>HfAl and Ni<sub>2</sub>TaAl, Ni atoms are found to contribute more in the same region. The vibrational properties and mode Grüneisen parameter confirm the stability of these compounds till high pressure and we proceed further to analyze the superconductivity of Ni<sub>2</sub>NbAl.

### 3.4. Superconductivity of Ni<sub>2</sub>NbAl

It is well known from the earlier studies that the FS topology change under pressure can be related to many other changes in the physical properties of the compounds [25, 26, 27, 28, 29, 30]. Among all the above mentioned compounds Ni<sub>2</sub>NbAl is reported to be a superconductor, with a superconducting transition temperature ( $T_c$ ) to be around 2.1 K. We have also calculated  $T_c$  for Ni<sub>2</sub>NbAl and found the value to be around 3.1 K with electron-phonon coupling constant ( $\lambda_{ep}$ ) to be 0.76 and  $\omega_{ln}$  (logarithmically averaged phonon frequency) to be 70.94 cm<sup>-1</sup> using Allen-Dynes [39] formula as given in equation (6) by considering the value of  $\mu^*$  (Coulomb pseudopotential), to be 0.15. Our calculated value of  $\lambda_{ep}$  slightly overestimate the earlier reported experimental value of 0.52 [11].

$$T_c = \frac{\omega_{ln}}{1.2} \exp\left(-\frac{1.04(1 + \lambda_{ep})}{\lambda_{ep} - \mu^*(1 + 0.62\lambda_{ep})}\right) \quad (6)$$

and

$$\lambda_{ep} = \frac{N(\epsilon_f)\langle I^2 \rangle}{M\langle \omega^2 \rangle} \quad (7)$$

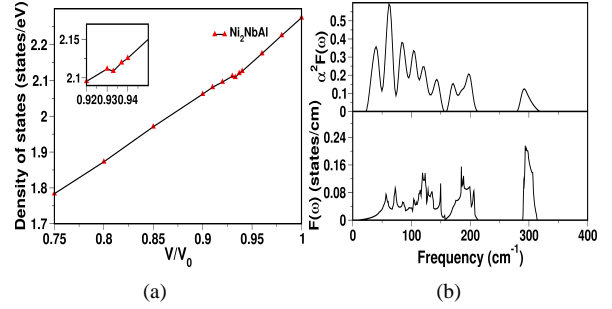


Figure 6: (color online) (a) Density of states at the Fermi level  $N(E_F)$  under compression (b) Eliashberg function  $\alpha^2 F(\omega)$  and phonon-density of states for Ni<sub>2</sub>NbAl compound.

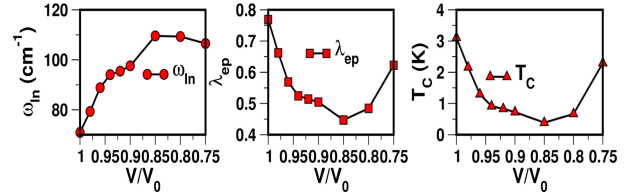


Figure 7: (color online) Logarithmically averaged phonon frequency ( $\omega_{ln}$ ), electron-phonon coupling constant ( $\lambda_{ep}$ ) and transition temperature ( $T_c$ ) for Ni<sub>2</sub>NbAl compound under compression.

where  $N(\epsilon_f)$  = electron density of states,  $\langle I^2 \rangle$  = mean square of electron-ion interaction,  $M$  = atomic mass and  $\langle \omega^2 \rangle$  = average of square of phonon frequency.

As stated above, under compression, we find a new electron pocket to appear in Ni<sub>2</sub>NbAl at around  $V/V_0 = 0.93$ , which enable us to throw light on the prediction of  $T_c$  under pressure. From our earlier work on superconductors [25, 26], we could expect a non-monotonic variation of density of states in the compounds, where we observe a FS topology change, which prompt us to search for the same in the present compound also and the density of states variation as a function of relative volume is shown in Fig.6(a) which presents a non-monotonic trend. Apart from this we have also plotted the Eliashberg function ( $\alpha^2 F(\omega)$ ) in Fig.6(b), where we find the Eliashberg function to be highest in the lower frequency region indicating Ni atom to contribute more for  $T_c$  as evident from the partial phonon density of states from the Fig.5(e). In addition we have also calculated the  $T_c$  under compression and find  $T_c$  to decrease initially, followed by an increase in accordance with the electron phonon coupling constant as shown in Fig.7. Apart from this we have also plotted the variation of  $\omega_{ln}$  as a function of pressure and find  $\omega_{ln}$  to increase initially and then to decrease under pressure which according to the formula (7), implies an inverse proportionality with

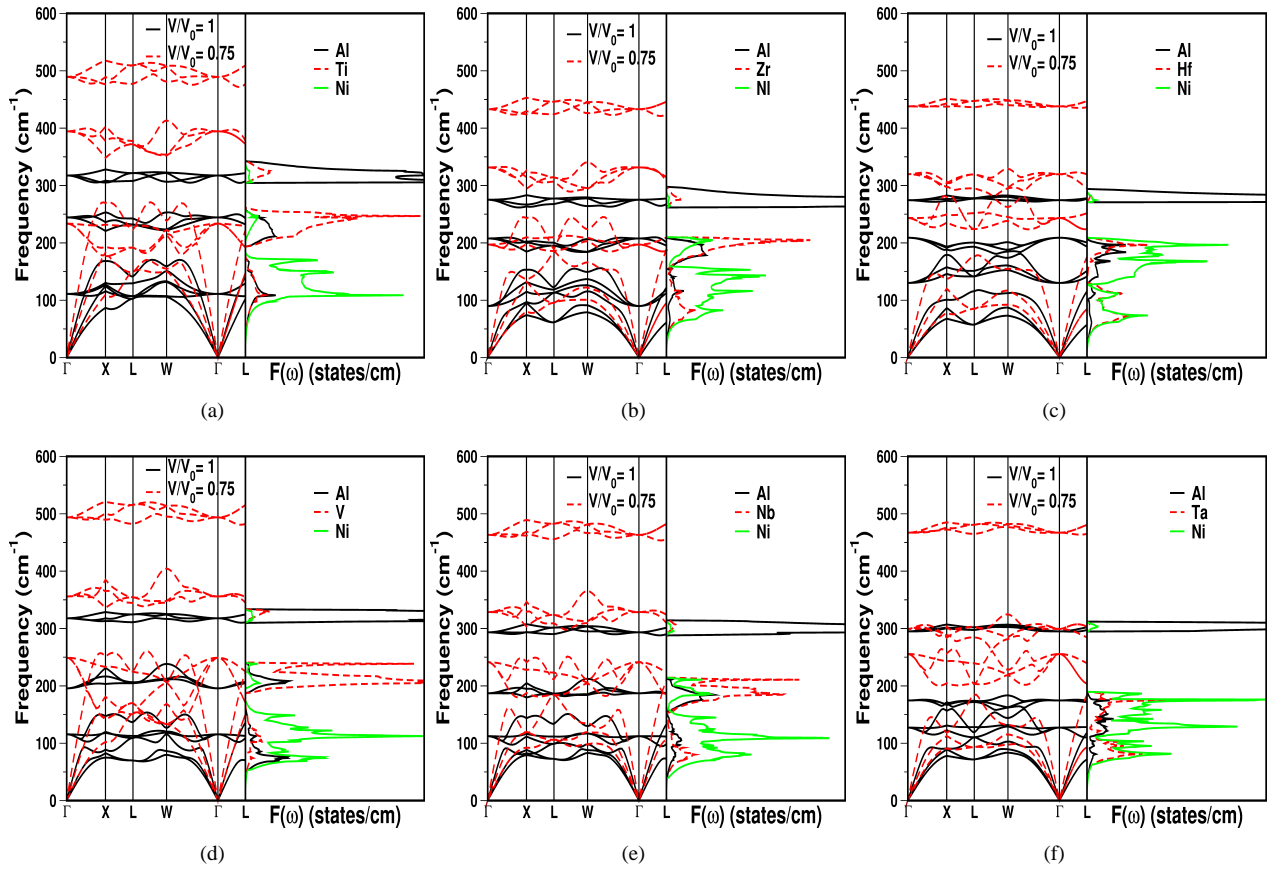


Figure 5: (color online) Phonon dispersion at ambient (solid line) and under compression (at  $V/V_0 = 0.75$ , where  $V_0$  is the experimental volume) along with phonon density of states ( $F(\omega)$ ) (at ambient) for (a)  $\text{Ni}_2\text{TiAl}$  (b)  $\text{Ni}_2\text{ZrAl}$  (c)  $\text{Ni}_2\text{HfAl}$  (d)  $\text{Ni}_2\text{VAl}$  (e)  $\text{Ni}_2\text{NbAl}$  (f)  $\text{Ni}_2\text{TaAl}$ .



$\lambda_{ep}$  and it is shown in Fig.7. Further, the variation of  $T_c$  under pressure, almost follows the same trend as that of  $\lambda_{ep}$ , which might enable us to predict that phonon contribution may be dominant in this compound.

### 3.5. Thermodynamic properties

To investigate the thermodynamic properties of  $\text{Ni}_2\text{XAl}$ , we have used quasi-harmonic approximation as implemented in Quantum Espresso [37]. In this approximation Helmholtz free energy at a given volume  $V$  and temperature  $T$  is given as

$$F(V, T) = U_0(V) + F_{vib}(V, T) \quad (8)$$

Where  $U_0$  is the the energy corresponding to zero temperature, and  $F_{vib}$  represents the vibrational contribution and it can be written as

$$F_{vib}(V, T) = \frac{1}{2} \sum_{n,q} \hbar w(n, q) + K_B T \sum_{n,q} \ln(1 - e^{-\hbar w(n,q)/K_B T}) \quad (9)$$

The frequency of the  $n^{\text{th}}$  mode,  $w(n, q)$ , depends on the unit cell volume and the masses of the constituent atoms. The calculated thermodynamic properties like specific heat at constant volume ( $C_V$ ), entropy ( $S$ ) and internal energy ( $U$ ) are shown in Fig.8,9.

The temperature dependence of internal energy, vibrational free energy, entropy and heat capacity at constant volume are shown in Fig.8 at ambient with temperature ranging from 0 K to 500 K. We have observed that the temperature variation of these thermodynamic functions exhibit almost a similar trend for all investigated compounds. The results of the internal energy from Fig.8(a) suggest that, above 200 K, the total internal energies increase almost linearly with temperature for all the compounds. At high temperatures the internal energy tends to display  $k_B T$  behavior. Fig.8(b) shows the variation of vibrational free energy as a function of temperature for the same compounds. Overall, free energy profiles of all the studied compounds show similar characteristics and the free energy  $F = U - TS$ , where  $U$  is internal energy and  $S$  is entropy, decreases gradually with increasing temperature. This is because of the fact that both  $U$  and  $S$  increases with temperature which lead to the decrease in free energy [52]. The free energy and internal energy at zero Kelvin temperature represent the zero point motion of the compounds. The calculated values of the free and internal energies for the compounds are close to each other and  $\text{Ni}_2\text{TiAl}$  have the highest value and  $\text{Ni}_2\text{ZrAl}$  have the lowest values at zero point temperature. The free energy calculations indicate that  $\text{Ni}_2\text{TiAl}$  is thermodynamically stable. The variation of entropy with temperature for all these compounds in

the same temperature range is given in Fig.8(c). From this figure we have observed that at 0 K the entropies are zero for all compounds and the entropy change increase rapidly as temperature increases. At above 350 K the variation of entropy is small. This change in entropy is due to the increase of the vibrational motion of the atoms with temperature leading to the increase in the internal energy of the system. From this figure we observe that  $\text{Ni}_2\text{TiAl}$  have the minimum entropy values, which indicate  $\text{Ni}_2\text{TiAl}$  to be highly ordered in comparison with other compounds. The specific heat capacity is a measure of how well the substance stores the heat. The calculated specific heat as a function of temperature for all the investigated compounds are shown in Fig.8(d). From this we can clearly see that at high temperatures the specific heat at constant volume obeys Dulong Petit limit, and at low temperatures it is proportional to  $T^3$  law. At the intermediate temperatures, the temperature dependence of specific heat is governed by the details of vibrations of the atoms. From this figure we have observed that  $\text{Ni}_2\text{TiAl}$  has the lowest value of specific heat compared to other compounds.

To explore further we have also calculated the bulk modulus ( $B$ ), which measures the resistance of the substance to uniform compression and linear thermal expansion ( $\alpha$ ) as a function of temperature. The calculated temperature variation of bulk modulus ( $B$ ) is given in Fig.9(a). From the figure we can see the bulk modulus to decrease with increase in temperature for all the compounds studied. The calculated values of linear thermal expansion coefficient ( $\alpha$ ) as a function of temperature is shown in Fig.9(b). From this figure, we observe that all the compounds show positive thermal expansion coefficient and at high temperatures, the compounds containing IV-B group elements possess higher  $\alpha$  values than the compounds containing V-B group elements. Among all the compounds at high temperatures  $\text{Ni}_2\text{TiAl}$  has the highest  $\alpha$  value whereas  $\text{Ni}_2\text{TaAl}$  is found to have the lowest  $\alpha$  value.

## 4. Conclusions

We have studied the electronic, mechanical, vibrational, thermodynamical and Fermi surface properties of all the investigated compounds using first principles calculations. The obtained structural parameters are in good agreement with the experimental and other theoretical data at ambient condition. Under compression we find an extra band to cross the  $E_F$  in the case of  $\text{Ni}_2\text{NbAl}$  resulting in a new electron pocket at X-point.  $\text{Ni}_2\text{NbAl}$  is found to be a superconductor

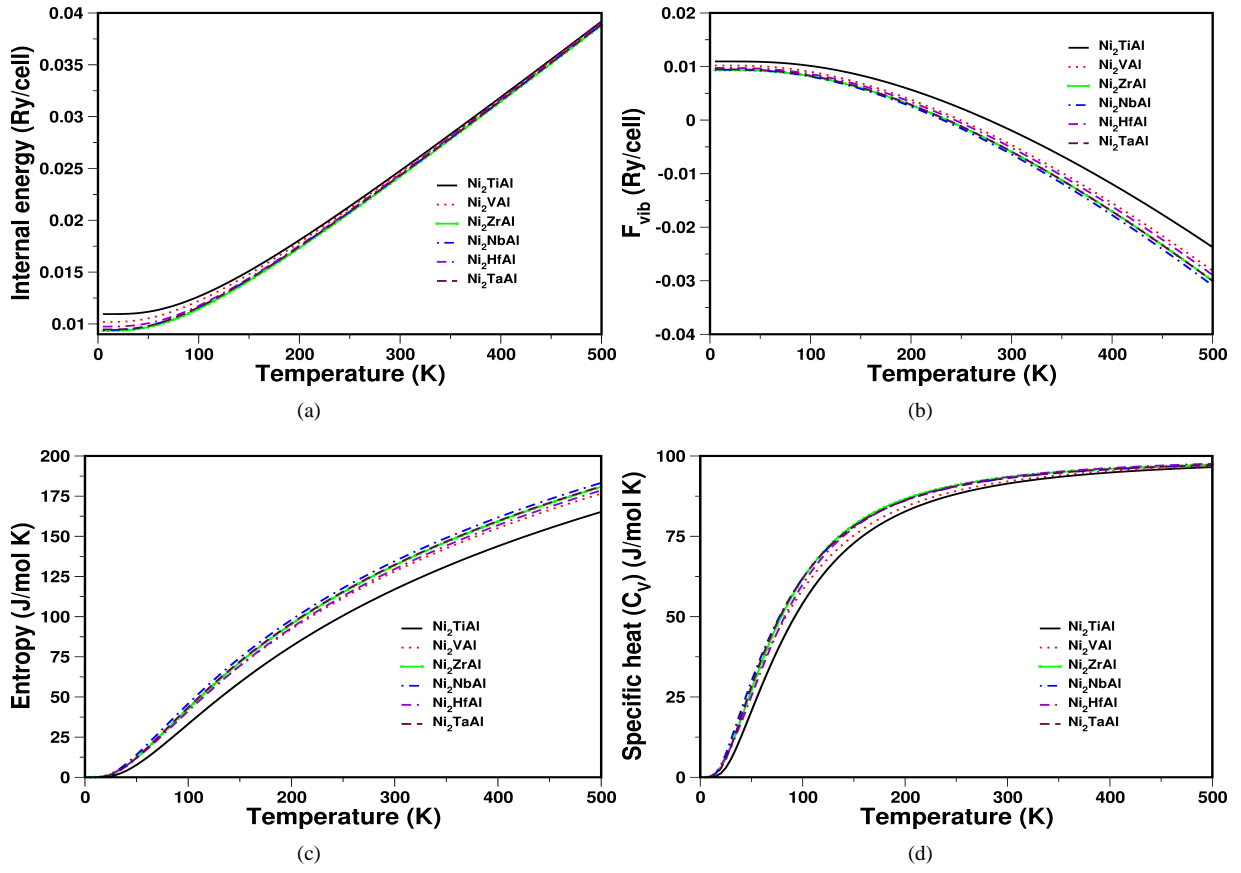


Figure 8: (color online) Variation of thermodynamic properties with temperature at ambient (at  $V/V_0 = 1.00$ , where  $V_0$  is the experimental volume) (a) Internal energy (b) Vibrational free energy (c) Entropy (d) Specific heat.

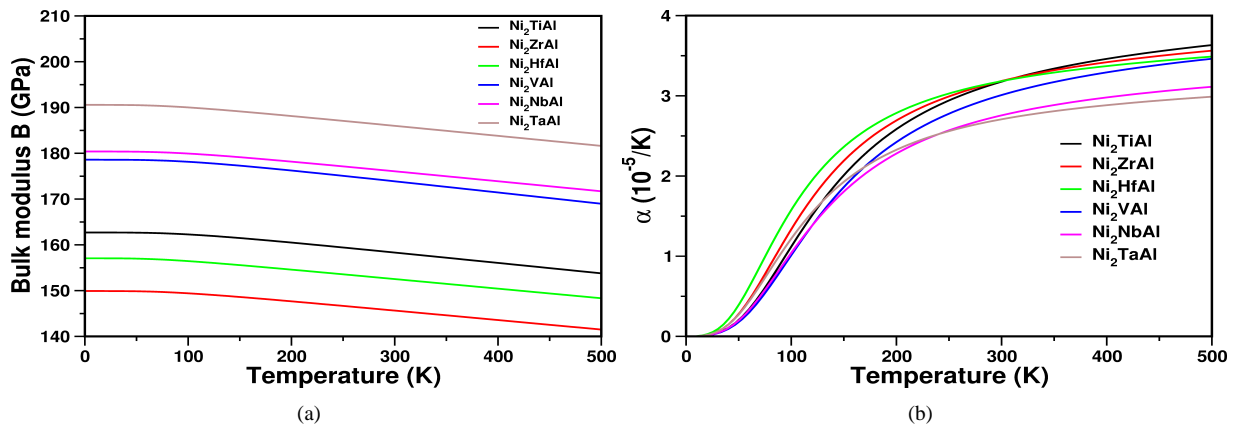


Figure 9: (color online) (a) Variation of bulk modulus with temperature (b) linear thermal expansion coefficient Ni<sub>2</sub>XAl (X=Ti, Zr, Hf, V, Nb, Ta) as a function of temperature.

with  $T_c$  around 3.1 K in good agreement with exper-  
 iment. A non-monotonic variation in the DOS is ob-  
 served in  $Ni_2NbAl$ , which may further indicate a non-  
 monotonic variation of  $T_c$  under pressure, which is also  
 observed from the present calculations. From elastic  
 constants and the related mechanical properties, we find  
 all the compounds to be ductile in nature with elastic  
 anisotropy. Apart from this, the mechanical and the dy-  
 namical stability of these compounds are verified from  
 our calculated elastic constants and the phonon disper-  
 sion relation, respectively. The phonon hardening ob-  
 served in all the compounds under compression is also  
 confirmed from the calculated mode Grüneisen param-  
 eter. Among all the investigated compounds,  $Ni_2TiAl$   
 has the lowest specific heat and entropy, and highest in-  
 ternal energy, vibrational free energy and linear thermal  
 expansion coefficient, which might enable  $Ni_2TiAl$  to  
 find promising applications.

## Acknowledgments

The authors would like to thank Department of Sci-  
 ence and Technology (DST) for the financial sup-  
 port through SR/FTP/PS-027/2011. The authors would  
 also like to acknowledge IIT-Hyderabad for providing  
 the computational facility. V.K acknowledge "NSFC  
 awarded Research Fellowship for International Young  
 Scientists under Grant No. 11250110051".

## References

- [1] T. Graf, C. Felser, S.S.P. Parkin, *Progress in Solid State Chem-*  
*istry* 39 (2011) 1.
- [2] W. Lin, A.J. Freeman, *Phys. Rev. B* 45 (1992) 61.
- [3] P.R. Strutt, R.S. Polvani, J.C. Ingram, *Metal. Mat.Trans. A* 7A  
 (1976) 23.
- [4] A. Taylor, R.W. Floyd, *J. Inst. Met.* 81 (1952) 25.
- [5] Y. Umakishi, M. Yamaguchi, T. Yamane, *Phil. Mag. A* 52 (1985)  
 357.
- [6] A. Raman, K.Schubert, *Z. Metallik.* 56 (1965) 99.
- [7] F.S. Da Rocha, G.L.F. Fraga, D.E. Brandao, C.M. Da Silva, A.A.  
 Gomes, *Physica B* 269 (1999) 154.
- [8] J. Sahariya, B.L. Ahuja, *Phys. B* 407 (2012) 4182.
- [9] E. Shreder, S.V. Streltsov, A. Svyazhin, A. Makhnev, V.V.  
 Marchenkov, A. Lukoyanov, H. W.Weber, *J. Phys.: Condens.*  
*Matter.* 20 (2008) 045212.
- [10] Y. Miura, M. Shirai, K. Nagao, *J. App. Phy.* 99 (2006) 08J112.
- [11] S. Waki, Y. Yamaguchi, K. Mitsugi, *J. Phys. Soc. Jpn.* 54 (1985)  
 1673.
- [12] R. Darolia, *Journal of the Minerals, Metals and Materials Soci-*  
*ety* 43 (1991) 44.
- [13] A.I. Taub, *Fleischer, Science* 243 (1989) 616.
- [14] R.L. Fleischer, *Platinum Metals Rev.* 36 (1992) 138.
- [15] M. Yamaguchi, H. Inui K. Ito, *Acta Mater.* 48 (2000) 307.
- [16] D.G. Morris, M.A. Muñoz-Morris, *Rev. Metal. Madrid. Vol.*  
*Extr.* 498 (2005).

- [17] J. Winterlik, G.H. Fecher, A. Thomas, C. Felser, *Phys. Rev. B*  
 79 (2009) 064508.
- [18] K. Ramesh Kumar, V. Chunchu, A. Thamizhavel, *J. Appl. Phy.*  
 113 (2013) 17E155.
- [19] T. Klimczuk, C.H. Wang, K. Gofryk, F. Ronning, J. Winterlik,  
 G.H. Fecher, J.-C. Griveau, E. Colineau, C. Felser, J.D. Thomp-  
 son, D.J. Safarik, R.J. Cava, *Phys. Rev. B* 85 (2012) 174505.
- [20] W. Ming, Y. Liu, W. Zhang, J. Zhao, Y. Yao, *J. Phys.: Condens.*  
*Matter.* 21 (2009) 075501.
- [21] S. Picozzi, A. Continenza, A.J. Freeman, *J. Phys. D: Appl. Phys.*  
 39 (2006) 851.
- [22] A.T. Zayak, P. Entel, K.M. Rabe, W.A. Adeagbo, M. Acet, *Phy.*  
*Rev. B* 72 (2005) 054113.
- [23] G.T. De Laissardiere, D.N. Manh, L. Magaud, J.P. Julien, F.  
 Cyrot-Lackmann, D. Mayou, *Phys. Rev. B* 52 (1995) 7920.
- [24] H Fu, D. Chen, X. Chenga, T. Gao, X. Yang, *Physica B* 388  
 (2007) 303.
- [25] S. Ram, V. Kanchana, G. Vaitheeswaran, A. Svane, S.B. Dug-  
 dale, N.E. Christensen, *Phys. Rev. B* 85 (2012) 174531.
- [26] S. Ram, V. Kanchana, A. Svane, S.B. Dugdale, N.E. Chris-  
 tensen, *J. Phys.: Condens. Matter.* 25 (2013) 155501.
- [27] S. Huang, C.W. Chu, F.Y. Fradin, L.B. Welsh, *Solid State Com-*  
*mun.* 16 (1975) 409.
- [28] A. Landa, J. Klepeis, P. Soderlind, I. Naumov, O. Velikokhatnyi,  
 L. Vitos, A. Ruban, *J. Phys.: Condens. Matter.* 18 (2006) 5079.
- [29] H. Rosner, D. Koudela, U. Schwarz, A. Handstein, M. Hanfland,  
 I. Opahle, K. Koepernik, M.D. Kuzmin, K.H. Muller, J.A. My-  
 dosh, M. Richter, *Nature Phys.* 2 (2006) 469.
- [30] D. Koudela, M. Richter, A. Möbius, K. Koepernik, H. Eschrig,  
*Phy. Rev. B* 74 (2006) 214103.
- [31] P. Blaha, K. Schwarz, P. Sorantin, S.B. Tricky, *Comp. Phys.*  
*Comm.* 59 (1990) 399.
- [32] P. Blaha, K. Schwarz, G.K.H. Madsen, D. Kvasnicka, J. Luitz, In:  
 K. Schwarz, editor. WIEN2k, an augmented plane wave plus  
 local orbital programe for calculating crystal properties. Aus-  
 tria: Tech. Techn. Universität wien, Austria, ISBN 3-9501031-  
 1-2;2001.
- [33] J.P. Perdew, K. Burke, M. Ernzerhof, *Phys. Rev. Lett.* 77 (1996)  
 3865.
- [34] H.J. Monkhorst, J.D. Pack, *Phys. Rev. B* 13 (1976) 5188.
- [35] P.E. Blochi, O. Jepsen, O.K. Andersen, *Phy. Rev. B* 49 (1994)  
 16223.
- [36] F. Birch, *Phys. Rev.* 71 (1947) 809.
- [37] P. Giannozzi, S. Baroni, N. Bonini, M. Calandra, R. Car, C.  
 Cavazzoni, D. Ceresoli, G.L. Chiarotti, M. Cococcioni, I. Dabo,  
 A.D. Corso, S. de Gironcoli, S. Fabris, G. Fratesi, R. Gebauer,  
 U. Gerstmann, C. Gougoussis, A. Kokalj, M. Lazzeri, L. Martin-  
 Samos, N. Marzari, F. Mauri, R. Mazzarello, S. Paolini, A.  
 Pasquarello, L. Paulatto, C. Sbraccia, S. Scandolo, G. Sclauzero,  
 A.P. Seitsonen, A. Smogunov, P. Umari, R.M. Wentzcovitch, *J.*  
*Phys.: Cond. Matt.* 21 (2009) 395502.
- [38] S. Baroni, S.D. Gironcoli, A. dal Corso et. al., (2008); [http :  
 //www.pwscf.org](http://www.pwscf.org).
- [39] P.B. Allen, R.C. Dynes, *J. Phys. C: Solid State Phys.* 8 (1987)  
 L158.
- [40] A. Otero-de-la-Roza, V. Luaña, *Comp. Phys. Commun.* 182  
 (2011) 1708.
- [41] E Şaşıoğlu, I Galanakis, C Friedrich and S Blügel, *Phy. Rev. B*  
 88 (2013) 134402.
- [42] M Born, *J. of Chem. Phys.* 7 (1939) 591.
- [43] R. Hill, *Proc. Phys. Soc. A* 65 (1952) 349.
- [44] V. Kanchana, *Euro. Phys. Lett.* 87 (2009) 26006.
- [45] V. Kanchana, G. Vaitheeswaran, Ma Yanming, Yu Xie, A.  
 Svane, O. Eriksson, *Phys. Rev. B* 80 (2009) 125108.
- [46] V. Kanchana, G. Vaitheeswaran, A. Svane, A. Delin, *J. Phys.:*

- Condens. Matt. 18 (2006) 9615.
- 585 [47] V. Kanchana, G. Vaitheeswaran, A. Svane, J. Alloy. Comp. 455  
(2008) 480.
- [48] S.F. Pugh, Philos. Mag. 45 (1954) 823.
- [49] J.J. Wortman, R.A. Evans, J. App. Phy. 36 (1965) 153.
- [50] C. Bungaro, K.M. Rabe, A. Dal Corso, Phy.Rev. B 68 (2003)  
590 134104.
- [51] S.A. Ostanin, V. Yu. Trubitsin, S.Yu. Savrasov, M. Alouani, H.  
Dreyse, Comp. Mater. Sci. 17 (2000) 202.
- [52] K. Ramesh Babu, Ch. Bheema Lingam, S. Auluck, S.P. Tewari,  
G. Vaitheeswaran, J. Solid. State Chem. 184 (2011) 343.